

Solar Reflectance Index of Pedestrian Pavements and Their Response to Aging

N. L. Alchapar, E. N. Correa, and M. A. Cantón

Abstract—Due to the impact of the optical characteristics of the materials composing the urban envelopes on the energy balance of cities, their categorization according to their ability to decrease urban temperatures is an indispensable tool for sustainable development. This work presents the evaluation results of the thermal performance of the different pedestrian pavements available in the region, so as to classify them according to the Solar Reflectance Index (SRI). The study was carried out during a 2-year period, involving the analysis of the behaviour of 28 pavements in widely used compositions, shapes and colours. Additionally, the aging effect of the material was quantified over the SRI. The results show that 74% of pavements diminished their initial ability for decreasing temperatures, while 50% of the dark material, with initial negative performances, improved their thermal behavior.

Index Terms—Aging, solar reflectance index, optical properties of materials.

I. INTRODUCTION

Just as materials have been traditionally characterized according to their mechanical, electrical or magnetic properties, this study proposes to characterize them according to their optical properties, expressed by means of the Solar Reflectance Index (SRI), in order to evaluate their energy-environmental behavior in an urban medium.

High Solar Reflectance Index (SRI) materials do not raise their temperature much when exposed to sun radiation. In cities, the use of cold materials is a passive cooling strategy appropriate for preventing excessive heat increase and accumulation. This also enables the improvement of urban space habitability in terms of comfort and decreasing the air-conditioning consumption in buildings, thus allowing a rational use of energy and contributing to environmental sustainability [3], [4], [8]. Albedo (\hat{a}) and thermal emittance (ϵ) are important factors which affect the surface temperature of the material and the air temperature close to the surface. Surfaces with low solar reflectance absorb a greater fraction of incident solar energy [2], [5], [7], [9], [10].

A fraction of this energy goes into the ground and buildings, another fraction is transmitted by convection to the air (leading to an increase of air temperature), and the last one is radiated to the sky [1]. In equivalent conditions, a surface

with less emissivity will radiate in less proportion and cool less, therefore presenting higher temperatures [2].

Thus the determination of solar reflectance, thermal emittance (ϵ) and the relative temperature of surfaces (T_s) with respect to the reference temperature of a black and white pattern (determined by the SRI) could help designers and consumers to choose adequate materials for energy consumption efficiency of buildings and communities.

II. METHODOLOGY











A. Cases of Study

The sample is made up of 38 pedestrian pavements frequently used in the local urban medium. The pavements were classified into four compositions: *Monolayer (mono)*: Concrete and Natural Stone, and *Bilayer (bi)*: Concrete-stone, and Concrete-calcareous.

TABLE I: MATERIAL CLASSIFICATION ACCORDING TO ITS COMPOSITION, COLOR AND TEXTURE.

LAYER	COMPOSITION	COLOR	TEXTURE
Mono	Concrete	Red Yellow	Rustic
	Natural Stone	Gray Black	Smooth
Bi	Concrete-stone	Travertine Red-multicolor Bordeau Jade Green	Rustic Smooth
	Concrete-calcareous	Black-withe Black-multicolor Murcia Black	Smooth

TABLE II: MATERIAL CLASSIFICATION ACCORDING TO ITS SHAPE.

	SHAPE				
Straight					
	Square	Single Line	Multi Line	Diagonal	
	Circular				
		Spider	Fan	Andalucia	
Flat					
	Mosaic	Start	Boulder		

The *monolayer (mono)* compositions are pieces made up of only one material: concrete or natural stone. However, the *bilayer (bi)* materials are made up of a concrete-calcareous layer and a concrete-stone layer.

In Tables I y II pedestrian pavements are classified according to their composition, color, texture and shape.

B. Experiment and Instrumentation Description

To analyze the thermal behaviour of these samples, they were arranged on a 7cm thick horizontal platform of expanded polystyrene located in the premises of the Centro Regional de Investigaciones Científicas y Técnicas, in

Manuscript received October 30, 2012; revised December 30, 2012. This work was supported by the Agencia Nacional de Promoción Científica y Tecnológica -ANPCYT- (National Agency for Scientific and Technological Promotion) provided funds for the research. Also the Consejo Nacional de Investigaciones Científicas y Técnicas -CONICET- (National Council of Scientific and Technical Researches).

The authors are with the Institute of Environmental and Social Sciences (INCHUSA)- Human Environment and Housing Laboratory. CONICET - CCT-Mendoza. CC. Argentina (e-mail: nalchapar@mendoza-conicet.gov.ar, correa@mendoza-conicet.gov.ar, macanton@mendoza-conicet.gov.ar).

Mendoza, Argentina.

The aging of the surfaces was estimated by registering the emissivity, surface temperature, solar radiation over horizontal surface and air temperature corresponding to 13.00 used to calculate the SRI according to the established regulations (ASTM E1980-11, 2011) [2].

The monitoring was carried out during the 2011 and 2012 summer seasons. Among the series of registered measurements, the data reported in this study corresponds to two days when meteorological variables present representative local climate conditions (March, 10th 2011 and February, 10th 2012). On March 10th, 2011 the registered sun radiation flux was 883.7 W/m², average air temperature 29.7°C, relative humidity 24.5% and average wind speed 2.0 m/s. On February 10th, 2012 the registered sun radiation flux was 929.9 W/m², an average air temperature of 28.3°C, 31.5% of relative humidity and 1.3 m/s of wind speed. In order to determine the value of albedo (\hat{a}), a Kipp & Zonen CMA11 albedometer was used. A temperature sensor with type T thermocouple associated with a U12 data logger hobbo was employed for the emissivity (ϵ) calculations in accordance with regulations ASTM E-1933-99^a [11], 2006. The surface thermal measurements (Ts) were taken with an IR Fluke Ti 55 camera (Table II).

C. SRI Calculation

The SRI is a composite value in a scale from 0 to 100 based on the reflectance and emittance (ϵ) of the material's surface. It is calculated using the equations in ASTM E1980-11 [12].

SRI quantifies the accumulated heat of material in relation to a black and white reference surface, under standard ambient conditions.

D. Calculation of SRI Difference between 2011 - 2012 Thermal Registers

In order to quantify the response of the thermal behavior of materials to aging, weather and dirt, the following formula was used:

$$SRI_2 - SRI_1 = \Delta SRI \quad (1)$$

where,

SRI_1 = initial Solar Reflectance Index;

SRI_2 = SRI of aged materials;

ΔSRI = Difference between SRI_1 and SRI_2 values.

To simplify the analysis a range of values was established to determine that the thermal behavior of material is stable when the SRI differences are lower than (\pm) 5% between both periods.

Aging is favorable when the initial SRI (SRI_1) is lower than the aged material's SRI (SRI_2). On the contrary, SRI_1 registers higher than SRI_2 were classified as materials whose ability to decrease urban temperatures falls when submitted to the passing of time, i.e. $\Delta SRI < -5\% = Degraded$; $\Delta SRI \leq (\pm) 5\% = Stable$; $\Delta SRI > 5\% = Improved$.

III. RESULTS

The SRI for pedestrian pavements was obtained through the calculations made according to the ASTM E1980-11

equations and parameters. Under the analyzed conditions, new material (SRI1), aged material (SRI2) and their corresponding differences (ΔSRI). (Table I y II).

TABLE III: ENUMERATION OF PEDESTRIAN PAVEMENTS STUDIED DURING THE FIRST AND SECOND YEAR, WITH THEIR RESPECTIVE ASSIGNED CODES; ALBEDO (\hat{a}), EMISSIVITY (ϵ), SOLAR REFLECTANCE INDEX ($SRI_1 - SRI_2$) IN PERCENTAGES; AND SRI DIFFERENCES (ΔSRI). (PART I)

Cod.	Layer		1° Year			2° Year			ΔSRI
	Mono	Bi	SRI_1 %	\hat{a}	ϵ	SRI_2 %	\hat{a}	ϵ	
P01	x		71	0.54	0.90	60	0.48	0.90	-11
		Concrete gray rustic circular fan							
P02	x		59	0.42	0.95	59	0.45	0.95	0
		Concrete black rustic circular spider							
P03	x		77	0.59	0.95	59	0.45	0.95	-18
		Concrete red rustic circular andalucia							
P04	x		71	0.55	0.90	54	0.41	0.95	-17
		Concrete red rustic circular fan							
P05	x		52	0.35	0.95	51	0.38	0.95	-1
		Concrete black rustic circular fan							
P06		x	73	0.57	0.90	56	0.43	0.95	-17
		Concrete-stone gray rustic flat boulder							
P07	x		55	0.39	0.95	51	0.38	0.95	-4
		Concrete black rustic straight square							
P08	x		79	0.62	0.90	61	0.47	0.95	-18
		Concrete gray rustic circular spider							
P09	x		74	0.57	0.90	58	0.44	0.95	-16
		Concrete red rustic circular spider							
P10		x	53	0.36	0.95	48	0.35	0.95	-5
		Concrete-stone murcia black smooth circular fan							
P11	x		72	0.56	0.90	57	0.43	0.95	-15
		Concrete-stone black-white smooth circular andalucia							
P12		x	54	0.38	0.95	56	0.42	0.95	2
		Concrete-stone murcia black smooth straight square							
P13		x	80	0.64	0.85	64	0.50	0.95	-16
		Concrete-stone gray-multicolor smooth circular andalucia							
P14	x		71	0.55	0.90	61	0.47	0.95	-11
		Concrete yellow rustic stright diagonal							
P15	x		61	0.44	0.95	58	0.44	0.95	-3
		Concrete red rustic flat mosaic							
P16		x	72	0.55	0.90	59	0.47	0.90	-13
		Concrete multicolor rustic flat boulder							
P17	x		75	0.58	0.90	58	0.44	0.95	-17
		Concrete yellow rustic flat start							
P18	x		73	0.56	0.90	55	0.41	0.95	-18
		Concrete gray rustic flat start							
P19	x		59	0.42	0.95	52	0.39	0.95	-7
		Concrete black rustic flat mosaic							

(PART 2)

Cod.	Layer		Description	1° Year			2° Year			Δ SRI
	Mono	Bi		SRI ₁	â	ε	SRI ₂	â	ε	
				%			%			
P20	x		Concrete gray rustic straight square	77	0.60	0.90	60	0.46	0.95	-17
P21		x	Concrete-stone jade green smooth circular andalucia	65	0.48	0.95	53	0.40	0.95	-12
P22	x		Concrete-stone black-white smooth straight square	55	0.38	0.95	51	0.38	0.95	-3
P23	x		Concrete-stone murcia black smooth circular	64	0.49	0.90	52	0.41	0.90	-12
P24	x		Concrete-stone bordeau smooth straight square	72	0.56	0.90	55	0.41	0.95	-17
P25	x		Natural Stone gray smooth flat mosaic	85	0.68	0.85	66	0.53	0.90	-18
P26	x		Concrete-stone black-multicolor smooth circular andalucia	85	0.67	0.90	59	0.45	0.95	-26
P27	x		Concrete black rustic circular andalucia	52	0.35	0.98	63	0.48	0.98	11
P28	x		Concrete-stone red smooth straight square	75	0.59	0.90	61	0.47	0.95	-14
P29	x		Natural Stone murcia black smooth flat mosaic	62	0.47	0.90	54	0.42	0.90	-8
P30	x		Concrete-stone gray-multicolor smooth straight square	76	0.59	0.90	66	0.53	0.90	-10
P31	x		Natural Stone jade green smooth flat mosaic	69	0.53	0.90	55	0.43	0.90	-14
P32	x		Concrete-stone jade green smooth straight square	69	0.53	0.90	53	0.40	0.95	-17
P33	x		Concrete black rustic straight square	59	0.43	0.95	55	0.42	0.95	-4
P34	x		Natural Stone travertine smooth flat mosaic	100	0.93	0.80	100	0.82	0.80	0
P35	x		Concrete-calcareous black smooth straight	58	0.42	0.95	64	0.50	0.95	6
P36	x		Concrete-calcareous red	72	0.56	0.90	56	0.42	0.95	-17
P37	x		Concrete-calcareous yellow smooth straight single line	69	0.53	0.90	56	0.42	0.95	-13
P38	x		Concrete-calcareous yellow smooth straight multi line	74	0.58	0.90	55	0.42	0.95	-19

Initially the materials analyzed show higher dispersion in their SRI values, clearly identified with a cut line in SRI=70%. This means that 58% of the evaluated materials

present an initial SRI in the 70-100% range, whereas the remaining 42% presents values between 69 and 50% (Fig. 1).

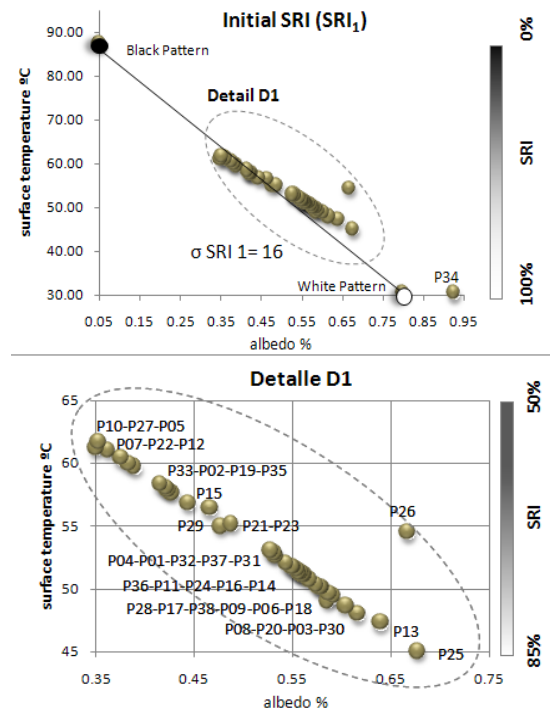


Fig. 1. Initial Solar reflectance index (SRI₁) according to surface temperature (°C) and albedo.

For aged materials (SRI₂) the cut line disappears and all materials are grouped in a 66-48% SRI range, which indicates that over 58% of the materials initially evaluated were efficient in their thermal response, and their performance worsened in just one year by 24%. Besides, it is clearly observable that the variable most affected by aging is albedo. Likewise, due to aging, surface temperatures in the studied cases had an approximate 7 to 11°C temperature increment. (Fig. 2 and Table III)

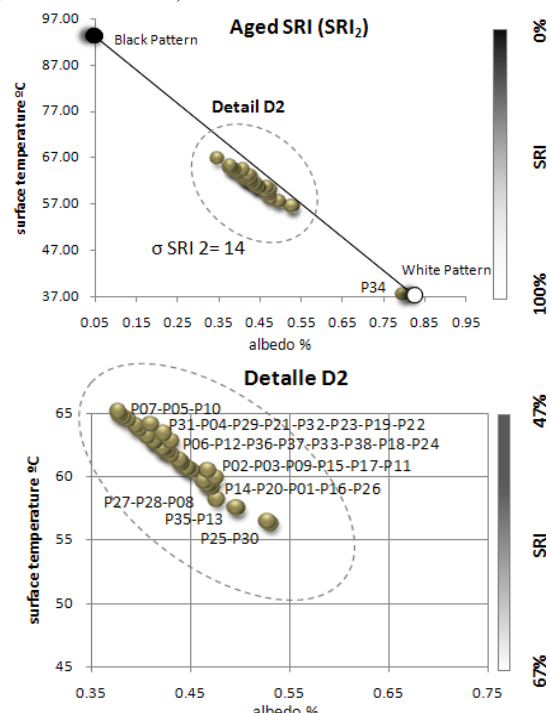


Fig. 2. Aged Solar Reflectance Index (SRI₂) according to surface temperature (°C) and albedo.

A. Solar Reflectivity Index Aging according to its Composition

After submitting the pavements to exterior weather conditions (aging), the *SRI* level differences were calculated for monolayer and bilayer materials. 70% of the monolayer materials and 78% of the bilayer decreased their thermal efficiency.

Within the stable materials there was 25% of monolayer and 11% of bilayer. Improvements of *SRI* higher to 15% were registered from which 5% correspond to monolayer and 10% to bilayer. (Fig. 3. and Table III).

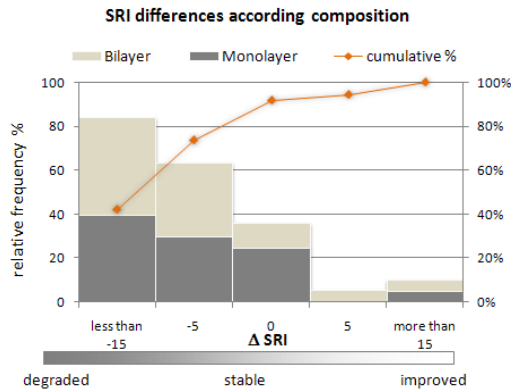


Fig. 3. Relative frequencies distribution (%) of *SRI* differences (ΔSRI) in pedestrian pavements according to composition.

B. Solar Reflectivity Index Aging According to its Shape

By analyzing the materials in isolation and according to their shape, it was observed that the most thermally inefficient is the flat one. That means 90% of the materials with this configuration have decreased their *SRI* between 7 and 18%.

The shapes that maintained their *SRI* stable to the passing of time, weather and dirt are the straight and circular, with a relative frequency of 21% in each case. 14% of straight pavements increased their *SRI* in a 5 to 15% range, improving their thermal conditions. (Fig. 4 and Table III).

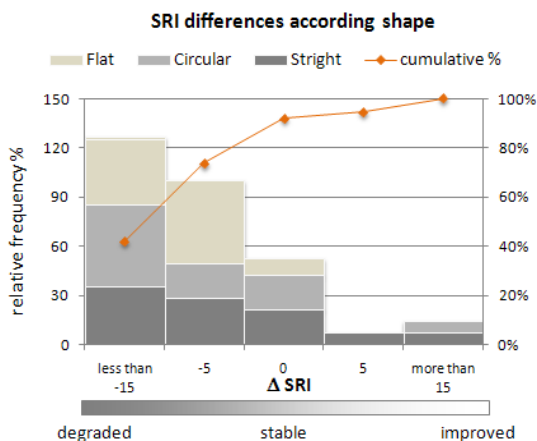


Fig. 4. Relative frequencies distribution (%) of *SRI* differences (ΔSRI) in pedestrian pavements according to shape.

C. Solar Reflectivity Index Aging according to its Colors

By separately analyzing the color variable for both compositions, we detected that 100% of the materials in gray, yellow, gray multicolor, travertine, red and black multicolor, and bordeaux decreased their *SRI* by 5 to 20%.

Within the colors that maintained a constant *SRI* through time are, firstly, the black and black-white pavements, since half (50%) the samples did not suffer wearing from open air exposure. Colors which increased the *SRI* were black (27%) and black-white (25%) by 6 to 15%. (Fig. 5 and Table III).

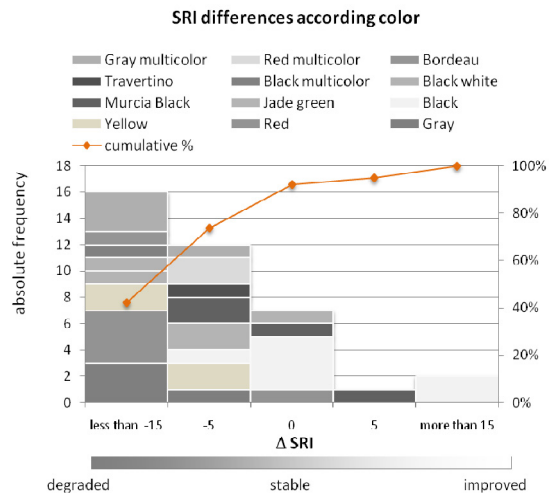


Fig. 5. Relative frequencies distribution (%) of *SRI* differences (ΔSRI) in pedestrian pavements according to color.

IV. CONCLUSION

Results show that the *SRI* is a useful indicator for categorizing the thermal behavior of a group of pedestrian pavement samples. 74% of the pedestrian pavements tend to decrease their *SRI* with time as a consequence of the wearing away produced by exterior conditions and dirt accumulation.

The most affected optical property was albedo. However, a group of materials showed an improvement according to their classification: monolayer composition, straight shape and black and black-white color.

Finally, most of the evaluated pavements decreased their *SRI* by 23% in just a year in response to aging. Therefore it is necessary to quantify the indicator variation through time so as to achieve a rigorous characterization of the evaluated material's thermal behavior.

REFERENCES

- [1] B. Givoni, *Passive and Low Energy Cooling of Building*, International Thomson Publishing, Inc. N.Y.: Wiley, 1994, pp. 1-36; 81-130.
- [2] D. Sailor and H. Fan, "Modeling the diurnal variability of effective albedo for cities," *Atmospheric Environment*, vol. 36, pp. 713-725.
- [3] G. Scudo and J. M. Ochoa, *Spazi Verdi Urbani. La Vegetazione Come Strumento Di Progetto Per Il Comfort Ambientale Negli Spazi Abitati*, Napoli: Sistemi Editoriali, 2003.
- [4] H. Akbari, S. Davis, S. Dorsano, J. J. Huang, and S. Winert, *Cooling our Communities- US Environmental Protection Agency*, Office of Policy Analysis, Climate Change Division, 1992.
- [5] J. Simpson and E. McPherson, "The effects of roof albedo modification on cooling loads of scale model residences in Tucson," *Energy and Buildings*, vol. 25, pp. 127-137, 1997.
- [6] K. Niachou, L. Livada, and M. Santamouris, "Experimental study of temperature and airflow distribution inside and urban street canyon during hot summer weather conditions.-Part I: Air and surface temperatures," *Building and Environment*, vol. 43, pp. 1383-1392, 2008.
- [7] M. Doulos, M. Santamouris, and I. Livada, "Passive Cooling of Outdoor urban spaces," *The Role of Materials. Solar Energy*, vol. 77, pp. 231-249, 2004.
- [8] M. Santamouris, A. Synnefa, and Karlessi, "Using Advanced Cool Materials in the Urban Built Environment to Mitigate Heat Islands and

Improve Thermal Comfort Conditions,” *Solar Energy*, vol. 85, pp. 3085-3102, 2007.

- [9] M. Santamouris, N. Papanikolaou, and C. Georgakis, “Internal Report. Group Building Environmental Studies, Physics Department,” University of Athens, Athens, Greece, 1998.
- [10] P. Araújo and F. Laurencó, “Measurement of Albedo and Analysis of Influence the Surface Temperature of Building Roof Materials,” *Energy and Buildings*, vol. 37, pp. 295-300, 2005.
- [11] *Standard Test Methods for Measuring and Compensating for Emissivity Using Infrared Imaging Radiometers*, ASTM E-1933-99a, 2006.
- [12] *Standard Practice for Calculating Solar Reflectance Index of Horizontal and Low-Sloped Opaque Surfaces*, ASTM E-1980-11, 2011.



N. L. Alchapar is graduate Mendoza University, Facultad de Arquitectura y Urbanismo, Mendoza, Argentina in 2004. Currently, PhD student in Science – area renewable energies – in the Salta National University of (UNSa), Salta, Argentina. Research fellow in the National Council of Scientific and Technological Research (CONICET) of Argentina, with place of work at the Laboratory for Human Environment and Housing (LAHV) of the Institute for Human, Social and Environmental Sciences (INCIHUSA-CONICET), in Mendoza, Argentina.

Her research focuses on the study of thermo-physical and optical properties of the materials of urban enveloping surface to mitigate the urban heat island. The main objective is to generate a valid tool to support decisions of urban design and sustainable building. The results have been published in national scientific journals and in proceedings of congresses on the subject.



E. N. Correa is with Chemical Engineer PhD in Science – area renewable energy – (2006). Doctoral Thesis Subject: Urban Heat Island. The case of Mendoza Metropolitan Area. University Professor and Tenured Researcher in the National Council of Scientific and Technological Research (CONICET) of Argentina, with place of work at the Laboratory for Human Environment and Housing (LAHV) of the Institute for Human, Social and Environmental Sciences (INCIHUSA-CONICET), in Mendoza, Argentina. The research activity is focused on the study of the microclimatic effect or urban infrastructures along their entire life cycle in arid zones urban contexts. The main objective is to contribute to the sustainable urban planning and growth. On this theme, research projects have been financed by national and international agencies. The results have been published in national and international scientific journals and in proceedings of congresses on the subject.



M. A. Cantón is with University Professor and Researcher in the National Council of Scientific and Technological Research (CONICET) of Argentina, with place of work at the Laboratory for Human Environment and Housing (LAHV) of the Institute for Human, Social and Environmental Sciences (INCIHUSA-CONICET), in Mendoza, Argentina.

The research activity is focused on the study of the open space as regulator of environmental conditions in arid zones urban contexts. The main objective is to conduct the urban and building development towards sustainability. On this theme, research projects have been financed by national agencies and by international cooperation. The results have been published in international scientific journals and in proceedings of congresses on the subject.